

The stronger the better is not necessarily the case for fasteners

By Bill Eccles, Bolt Science

Have you ever come across a situation in which a high strength, plated fastener has failed in a brittle manner? Hydrogen induced cracking of plated high strength fasteners is relatively common.

It is also common for the blame to be attached to some fault in the manufacturing process rather than the service environment in which the fastener is placed. Rather than a manufacturing flaw it could be due to the choice of the type of fastener, coupled with the service environment in which the fastener is placed, that is the root cause of the failure. This is not widely recognised.

Many fastener users, crudely put, think that 'stronger is better'. The thinking is that structural failure can be catastrophic not only in terms of material/replacement costs but also the indirect costs related to the loss of company reputation. By using a higher strength fastener, the assumption is that the risk of such a failure occurring will be reduced. But in regard to fasteners, given the adverse effect that hydrogen can have on high strength fasteners, stronger is often certainly not better.

With fasteners, brittle type failures can be especially troublesome since they can occur unexpectedly giving no warning. The most common type of brittle fracture in fasteners is due to the poisonous effects that hydrogen can have on the strength of some steels. The deleterious effect that hydrogen can have on steel was first reported in a paper to the Royal Society in 1875 by W. H. Johnson. Since that time the topic has been studied extensively but is still the subject of research and controversy.

Hydrogen induced cracking, commonly referred to as hydrogen embrittlement, can occur to high strength steels and certain other metals such as titanium and certain stainless steels. Atomic hydrogen can enter the material during the production process or during its service life (as a result of corrosion or hydrogen in the atmosphere) causing a catastrophic brittle fracture. This occurs at a stress level well below the yield strength of the fastener. Figure 1 shows a

M10 electroplated 12.9 socket head cap screw cracked under the head due to embrittlement. One of the characteristics of hydrogen embrittlement is that it may only affect a small proportion of a batch of fasteners.

This reduction of load carrying ability does not happen immediately the hydrogen enters the steel. Once atomic hydrogen is introduced at the surface of the part, there is a migration of the hydrogen over time to the grain boundaries, flaws and inclusions in the material. The effect of the hydrogen is to cause a reduction in the defect formation energy and a decrease in the inter-atomic bonding energy. Atomic hydrogen can also bind together to form hydrogen gas (H₂) whose pressure build-up at a crack tip can also have a deleterious effect. By these mechanisms a normally ductile material can behave in a brittle manner.



Figure 1: M10 electroplated 12.9 screw cracked under the head

With the fastener under stress (which usually means once it is tightened), cracks are initiated once the local concentration of hydrogen, at a particular defect, exceeds some critical value.

Brittle fracture of fasteners that have been exposed to hydrogen during the manufacturing process can occur, typically, between 1 and 24 hours following tightening. If a fastener fails in a brittle manner in some period following the first day subsequent to tightening, there is an increasing likelihood that the hydrogen was introduced into the steel from the environment rather than during the manufacturing process.

Essentially for a fastener to be affected by a brittle fracture due to hydrogen, there must be three factors present:

- 1) The fastener must have been introduced to hydrogen.
- 2) The material must be susceptible - generally the higher the tensile strength/hardness of the fastener, the greater is the risk from this type of brittle fracture.
- 3) The fastener must be subjected to a high tensile stress.

The stresses imposed into the fastener by the tightening process are usually sufficiently high given the other two factors being true.

The Venn diagram shown in Figure 2 illustrates the interaction of these three factors.

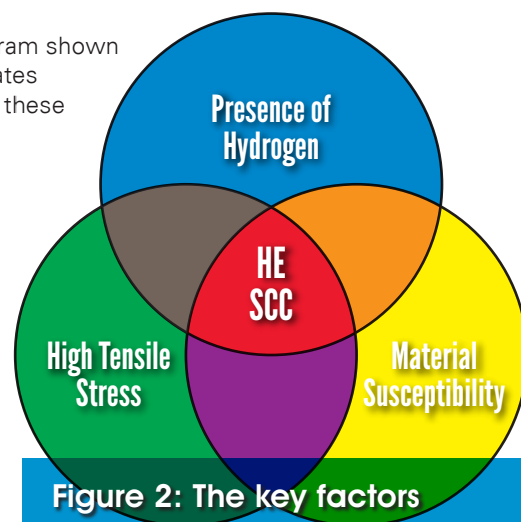


Figure 2: The key factors for HE and SCC

There are many ways that hydrogen can be introduced into the steel during the manufacturing process. The most common means is during the electroplating process. It can also be introduced from pickling, gas carburising, heat treatment and also during thread rolling, machining, and drilling due to the break-down of lubricants.

In many instances with fasteners the source of hydrogen contamination comes from the electroplating process. It is somewhat rare for non-electroplated fasteners to fail as a result of hydrogen embrittlement. On high strength electroplated fasteners, in order to reduce the risk of hydrogen embrittlement, a heat treatment operation immediately following plating can be performed. (This type of heat treatment is frequently referred to as baking.) The relevant standard giving guidance on the topic is ISO 4042 (Fasteners electroplated coatings). When high tensile fasteners are electroplated (property classes 10.9 and 12.9), a heat treatment operation is required within four hours of plating. Essentially the sooner the baking is completed following plating the better is the efficacy of the treatment. ▶

